

Processing Specification MaxiBridge Crimp Snap In

ERNI Electronics GmbH

Seestrasse 9 | 1 73099 Adelberg / Germany | +49 7166 50-0 | | www.erni.com

erstellt: Haegele, Ramona geprüft: Hippler, Christian

freigegeben: Entenmann, Oliver



Table of Contents

1. Notes, Terms and Abbreviations	3
2. Fundamentals	5
3. Product characteristics	5
4. Description	6
5. Requirements	
5.1. Cable Construction	
5.2. Conductor crimp according to IEC 60352-2	7
5.3. Insulation crimp	9
5.4. Terminal - Locking tab deformation	
5.5. Housing, crimp terminal and cable	10
5.6. Pull-out forces according to IEC 60352-2 respectively LV214 PG	10 11
5.7. Tear-off characteristics – informative – not an ERNI requirement	12
6. Assembly – single-row version	13
7. Assembly – dual-row version	15
8. Crimp terminal replacement	
9. Inspection	
9.1. Inspection of item characteristics	16

References

Attachment "Tools and Cables" Document # 074729 and # 074731

Change History

Change #	Change Description	Date (DE)
1	Crimp parameters 0,75 ²	11.10.2019
2	Article numbers of tooling for 0,752	09.04.2020
3	Explanations regarding tools & crimp parameters, wire utilization	13.11.2020
4	Various improvements incl. change of the document structure; processing parameters and other terminal-specific information moved to separate Attachment I	10.01.2022
5	With this edition the document focuses on contacts C2022 and C2426	10.02.2022
6	Extension of focus on C1820 and explanations about terminal-specific formation of the crimped region and related insights derived from stress tests	22.07.2022



1. Notes, Terms and Abbreviations

All processing strictly has to follow ERNI's Processing Specification in order to ensure best results.

ERNI reserves the right to apply changes to this document without prior notice.

The Processing Specification can be obtained by download from www.erni.com. The edition on the website is the latest release and replaces all older versions. Make sure you regularly check there for more recent issues. If there is no Processing Specification available online, please contact your local ERNI representative. This also applies to the Processing Specification's attachments which may change independently from the main Processing Specification.

Products and product information in this document are meant to be informative in nature and do not imply any assurance of performance or product properties, like availability, qualification, approval, or fit for a certain application, if not stated explicitly. For binding information inquire directly with ERNI.

The visualisations in this document are of a schematical nature and have been adjusted for their respective purposes. For exact product representations please refer to product drawings and CAD models, which can be found on our website (www.erni.com) or requested from ERNI directly.

All dimensions are specified in the unit millimeter (mm) if not explicitly stated otherwise.

"," (comma) may be used as a decimal delimiter instead of "." (period) in the course of this document and both are considered equal (2,1=2.1).

Six-digit numbers represent ERNI partnumbers in this document.

This document's contents have been written in a clear and distinct context. Therefore the specific product may not be named and PRODUCT or THE PRODUCT are used as placeholders.

MaxiBridge and MaxiBridge QT are independent product families that must not be confused or intermixed, and must clearly be distinguished.

Abbreviations

AWG American Wire Gauge

CSI Crimp Snap-In

Definition of Terms

Connector herein referring to a female / receptacle housing with or without terminals

if not otherwise noted

Contact herein referring to the front part of a terminal comprising its very "contact

range" meant to make contact with a pin contact

Cable used synonymically with (electrical) wire in the context of this document

Insulation holder the insulation crimp barrel or shorter the insulation crimp

Insulation support barrel -"Insulation holding device -"-

erstellt: Haegele, Ramona geprüft: Hippler, Christian freigegeben: Entenmann, Oliver 03.08.2022

Version 4 110 IMS Handbuch Seite 3 von 16

Integriertes Management System ERNI

5.3.4.4 MaxiBridge Processing Specification CSI en



Insulating grip effectiveness

The insulation crimp's capability to keep a wire's insulation

Insulator crimp insulation crimp

Pull-out strength refers to the capability of the terminal attached to a wire to withstand pull

forces (measured-value pull-out force)

Stranded wire wire with a conductor made from several, smaller wires

Terminal in the context of this document referring to a terminal with a crimp zone on

one end and a dual-beam receptacle contact design on the other end (also referred to as "contact range"), meant to make contact with a pin

contact

Termination refers to the side of the terminal that shall be crimped

Tear-off refers to breaking of the wire

Wire used synonymically with cable in the context of this document

References to Standards

DIN EN 60352-2 (international version IEC 60352-2)

Lötfreie Verbindungen - Teil 2: Crimpverbindungen - Allgemeine Anforderungen, Prüfverfahren und Anwendungshinweise; Deutsche Fassung EN 60352-2

[Solderless connections - Part 2: Crimped connections - General requirements, test methods and practical guidance; German version EN 60352-2]

LV 214 (OEM-specific equivalent VW 75174)

Kfz-Steckverbinder Prüfungen [Motor Vehicle Connectors Tests]

Informative References:

IPC-A-620 now IPC/WHMA-A-620

Requirements and Acceptance for Cable and Wire Harness Assemblies

VW 60330

Crimpverbindungen Lötfreie elektrische Verbindungen [Crimp Connections Solderless Electrical Connections]

DIN EN 60512-16-4 (international version IEC 60512-16-4)

Steckverbinder für elektronische Einrichtungen - Mess- und Prüfverfahren - Teil 16-4: Mechanische Prüfungen an Kontakten und Anschlüssen - Prüfung 16d: Zugfestigkeit von Crimpverbindungen;

[Connectors for electronic equipment - Tests and measurements - Part 16-4: Mechanical tests on contacts and terminations - Test 16d: Tensile strength (crimped connections)]

DIN EN 60512-16-8 (international version 60512-16-8)

Steckverbinder für elektronische Einrichtungen - Mess- und Prüfverfahren - Teil 16-8:

Mechanische Prüfungen an Kontakten und Anschlüssen - Prüfung 16h: Isolationshalterung bei Crimpverbindungen

[Connectors for electronic equipment - Tests and measurements - Part 16-8: Mechanical tests on connections and terminations - Test 16h: Insulating grip effectiveness (crimped connections)]

erstellt: Haegele, Ramona geprüft: Hippler, Christian

freigegeben: Entenmann, Oliver

03.08.2022 Seite 4 von 16



2. Fundamentals

The acceptance criteria for cable and harness assemblies in the current IPC-A-620 manual are generally recommended for the assembly of ERNI connectors.

3. Product characteristics

Crimp-Snap-In connectors of the MaxiBridge product family are available in various versions:

Number of pins of single-row connectors

2, 3, 4, 5, 6, 8, and 10-pin

Number of pins of dual-row connectors¹

10 and 20-pin

Crimp contact (terminal) sizes:

The crimp contacts (terminals) are available in following sizes and have been designed for their use in conjunction with the cross-sections listed here and single-wire termination. Double-wire crimps are not an intended use.

- Terminal "C2426" for AWG 24, 26 or 0,22 mm², 0,17 mm²
- Terminal "C2022" for AWG 20², 22 or 0,5 mm², 0,35 mm²
- Terminal "C1820" for AWG18 oder 0,75 mm².

Additionally, the above-mentioned information can be found in the respective attachments in detail.

Type of conductor crimp: B-crimp

Type of insulator crimp: wrap over (entwined crimp)

Thickness of contact base material: 0.3 mm

¹ Maximum diameter of the insulation for dual-row connectors: 1.55 mm (for details refer Attachment)


erstellt: Haegele, Ramona geprüft: Hippler, Christian freigegeben: Entenmann, Oliver 03.08.2022

Version 4 110 IMS Handbuch

² AWG 20 wires depending on the insulation diameter (refer Attachment)



4. Description

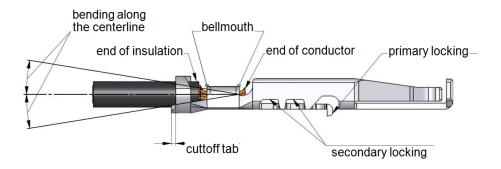

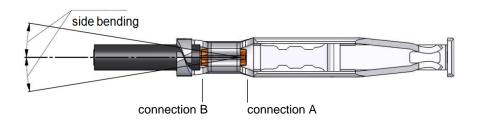


Figure 1

5. Requirements

5.1. Cable Construction

The requirements to the cable construction for crimp termination shall follow IEC 60532-2.

Within the scope of the IEC 60352-2 standard, cables need to meet following criteria in general:

- Stranded wires are to be used.
- It is not permitted to solder/dip solder stranded conductors (strands) within the area intended for the crimp connection.
- After crimping, no further soldering should take place.
- Soft-annealed copper with an elongation break of at least 10% is to be used.
- Bare copper or tin-plated (tin or tin-lead) or silver-plated single strands are to be used. The surface must be free from impurities or corrosion.
- The insulation must be easily removable from the conductor without changing the physical properties of the conductor.

Possible insulation diameter ranges are shown in Attachment I.

Information on approved wires can be found in Attachment I.

erstellt: Haegele, Ramona geprüft: Hippler, Christian

freigegeben: Entenmann, Oliver



5.2. Conductor crimp according to IEC 60352-2



Figure 2

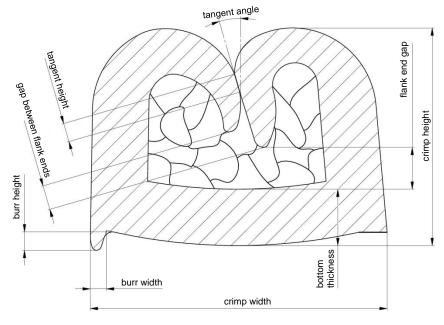


Figure 3
In addition to IEC 60352-2 following requirements apply to The Product:

- Crimp height:
- Crimp width:
- Pull-out force:
- Tangent angle:
- Tangent height:
- Flank end gap:
- Gap between flank ends:
- Burr height:
- Burr width:
- Bottom thickness:
- Filling:

Measured values, limits according to Attachment I Measured values, limits according to Attachment I Measured values, limits according to Attachment I max. 30°

min. 0.5 x terminal material thickness not permitted to touch the bottom

max. 1.0 x terminal material thickness

max. 1.0 x terminal material thickness

max. 0.5 x terminal material thickness

min. 0.75 x terminal material thickness

Strands must be completely pressed in a honeycombed structure. Individual cavities due to unsymmetrical forming or an unfavorable tolerance build-up of the material and the crimping height are still permissible as a borderline case (refer to below photo of a conductor crimp micro-section).

erstellt: Haegele, Ramona geprüft: Hippler, Christian

freigegeben: Entenmann, Oliver



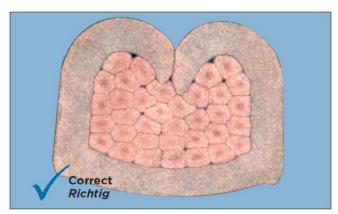


Figure 4

Formation of cracks at the bottom of the crimp barrel is not acceptable. Wrinkles which can occur at the inside of the rolled-in areas need to be distinguished.

To ensure a high current carrying capacity the contact was designed with a base material of a high thickness. Due to the material shift between the very conductor crimp range and the connection area towards the contact system ("connection A"), the formation of notches (wrinkles) is possible (refer Figure 5 – red circled areas). Based on the findings derived from stress tests this characteristic has no detrimental effect on the reliability of the terminal.







Figure 5



5.3. Insulation crimp



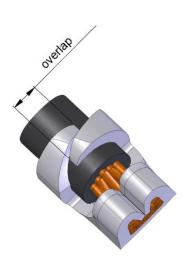


Figure 6

Requirements:

Insulation crimp height: Measured value, limits according to Attachment I
 Insulation crimp width: Measured value, limits according to Attachment I

Overlap of the crimp flanks at the wrap-over crimp (entwine-crimp):

min. 1.0 x terminal material thickness.

Insulations crimping: Minor deformation of the insulation surface respectively a minor penetration into the insulation

surface has to be achieved.

Ideally, the maximal deformation of 1/3 of the insulation thickness or the terminal material

thickness will not be exceeded.

Stronger deformation, especially with soft insulation materials; is permitted if the insulation is not damaged by cutting, piercing, or tearing.

Deviating from the standard's requirements, fully functional insulation crimp connections can be achieved without overlap of the crimp flanks. The prerequisite for doing so, is the achievement of the minimum pull-out force according to IEC 60352-2 or another relevant standard's limits applicable within the scope of customer-specific requirements (e.g. LV 214).

The insulation holder is not to be regarded as a strain relief. It shall firmly encompass the insulating sleeve but not penetrate it.

erstellt: Haegele, Ramona geprüft: Hippler, Christian

freigegeben: Entenmann, Oliver



5.4. Terminal - Locking tab deformation




Figure 7

Requirements:

- It is not permitted for the locking tab to be deformed inwards.
- Deformation outwards can reach a maximum of 2.2 mm.
- The locking tab must not be impaired in terms of the function.

5.5. Housing, crimp terminal and cable

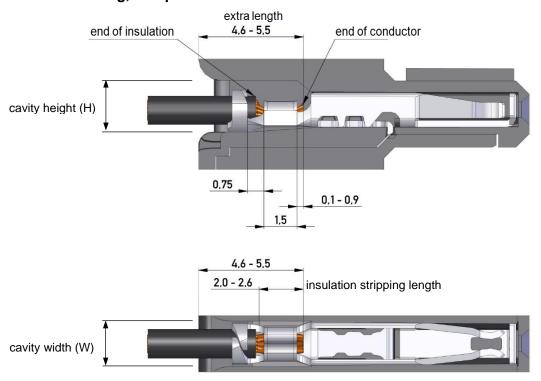


Figure 8

erstellt: Haegele, Ramona geprüft: Hippler, Christian

110 IMS Handbuch

freigegeben: Entenmann, Oliver

03.08.2022

Seite 10 von 16

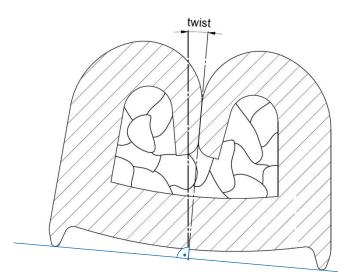


Figure 9

Requirements:

- The suitable insulation stripping length is 2.3 ± 0.3 mm (in Figure 8 dimension "2.0 2.6").
- The end of the conductor: 0.1 mm 0.9 mm past the end of the conductor crimp area.
- Projecting strands at connection A (front bellmouth towards contact range) are permitted
 provided all strands are contained in the conductor crimp and insertion of the terminal into
 the housing is not impaired.
- The end of the insulation must be visible between the insulation crimp and the conductor crimp; ideally located in the middle.
- A bellmouth on the cable entry side (connection B) must be recognizable. A bellmouth on the side of the conductor end (connection A) is permitted.
- "Side bending" must not exceed 3° (see Figure 1).
- "Bending along the centerline" must not exceed 5° (see Figure 1).
- "Twist" between crimp and contact range must not exceed 5° (see Figure 9, missing in Figure 1).
- The separating strip must not exceed 0.3 mm (see Figure 1).
- During processing the terminal extends its rear length. This extension must be limited to ≤ 0.4 mm.

5.6. Pull-out forces according to IEC 60352-2 respectively LV214 PG 10

Minimum pull-out forces are listed in Attachment I.

Seite 11 von 16



5.7. Tear-off characteristics – informative – not an ERNI requirement

The tear-off characteristics can be assessed as an optional criterion.

It is to be assessed positively, if the strands tear off irregularly behind the bellmouth once the required pull-out force (see Attachment I) has been achieved (refer Figure 10). The decisive criterion is pull-out force to reach or exceed the required value.

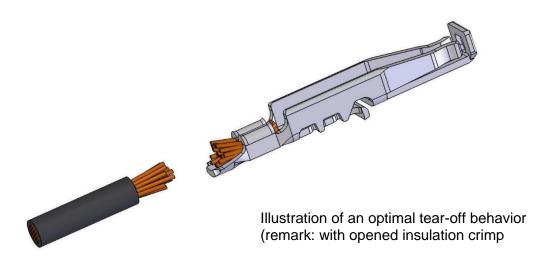


Figure 10

Indication:

The strands tear off directly behind the bellmouth: overpressed.

The strands do not tear off and are pulled out of the crimp: underpressed.

erstellt: Haegele, Ramona geprüft: Hippler, Christian

freigegeben: Entenmann, Oliver

03.08.2022


Seite 12 von 16



6. Assembly – single-row version

The single-row connector consists of housing with terminal cavities and locking member (secondary locking). When handling, please take note that housing and locking member do not lock unintentionally ahead of all terminals have been assembled into the housing.



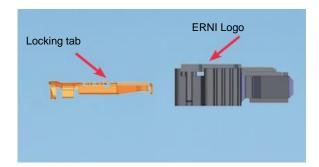

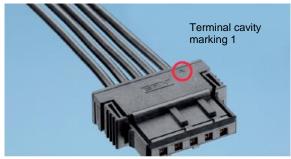


Figure 11

Populating of the terminal cavities with terminals is taking place in accordance with the work documents. The terminal must be inserted in correct orientation into the cavity until the primary locking audibly engages.

Correct engagement of the primary locking is to be checked by pulling backwards on the cable (max. 10N).

After complete terminal assembly, lock housing and secondary locking member by gently pressing them together. The secondary locking member shall fully engage and close.

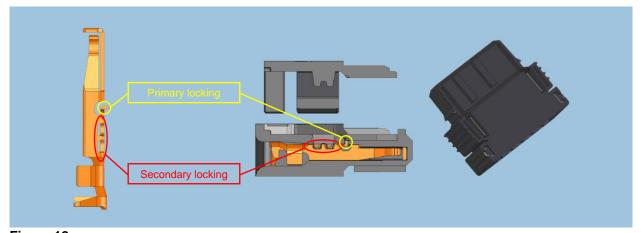


Figure 12

erstellt: Haegele, Ramona geprüft: Hippler, Christian

freigegeben: Entenmann, Oliver

Integriertes Management System ERNI





erstellt: Haegele, Ramona geprüft: Hippler, Christian


freigegeben: Entenmann, Oliver

Seite 14 von 16



7. Assembly – dual-row version

The dual-row connector consists of housing with terminal cavities and two locking members (secondary locking left and right). When handling, please take note that housing and locking are not locked unintentionally before all the terminals have been assembled.

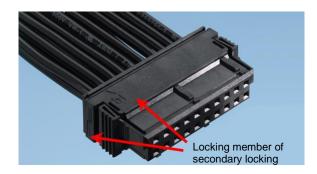

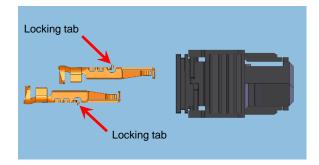




Figure 13

Populating of the terminal cavities with terminals is taking place in accordance with the work documents. The terminal must be inserted with correct orientation into the cavity until the primary locking is audibly engaged.

Correct engagement of the primary locking is to be checked by pulling backwards on the cable (max. 10N).

After complete terminal assembly, lock housing and secondary locking member by gently pressing them together. The secondary locking member shall fully engage and close.

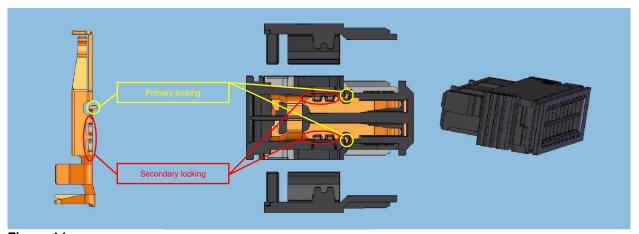


Figure 14

erstellt: Haegele, Ramona geprüft: Hippler, Christian

freigegeben: Entenmann, Oliver


03.08.2022


/ersion 4 110 IMS Handbuch




Only fully engaged locking members ensure a proper secondary locking function.

8. Crimp terminal replacement

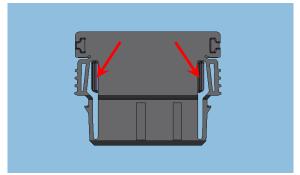



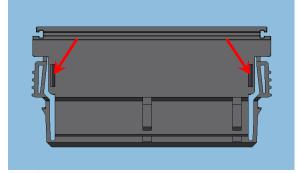

Dual-row connector

The interlock member (secondary locking) must be completely removed when replacing or removing a crimp terminal that already has been locked into the connector housing.

The single-row connector has one, while the dual-row connector has two secondary interlock members.

Regardless if the locking member is pre-engaged (delivery state) or already fully locked, by means of ERNI tool No. 464790 the two locking hooks shall be depressed (red arrows in above depictions).

The locking member can then be removed. A once opened connector housing shall not be reused and must be replaced by a new one.

Push down the locking tab (primary locking) using either ERNI tool partnumber 464790 or a small screwdriver and remove the terminal by pulling backwards on the cable.

The crimp terminal detached from the housing can be reused, however, it must be inspected for possible damage, especially for deformation of the primary locking tab and, if necessary, be replaced.

9. Inspection

9.1. Inspection of item characteristics

The requirements to both, wire and insulation crimp, are to be ensured by suitable variable and attributive tests.

erstellt: Haegele, Ramona geprüft: Hippler, Christian

freigegeben: Entenmann, Oliver

03.08.2022

Seite 16 von 16